



# HexPly<sup>®</sup> M18/1

180°C curing epoxy matrix

## Product Data

### Description

HexPly<sup>®</sup> M18/1 is a high performance, self extinguishing, tough epoxy matrix for use in primary aerospace structures. It exhibits low moisture absorption at saturation.


HexPly<sup>®</sup> M18/1 is a toughed epoxy resin system supplied with unidirectional and woven carbon fibres.

HexPly<sup>®</sup> M18/1 was developed as a controlled flow system to operate in environments up to 135°C.

### Benefits and Features


- Hot melt chemistry (nominal 180°C cure)
- Self extinguishing
- Very high temperature wet performances (135°C wet continuous service temperature)
- Low moisture absorption (0.74% after 1 week at 70°C 95% relative humidity (RH) and 3 weeks at 70°C 85% RH, measured on carbon fibre laminate)
- Flexible cure cycle (from 135°C to 210°C with or without post-cure)
- Specific cure cycle for vacuum bag

### Resin Matrix Properties

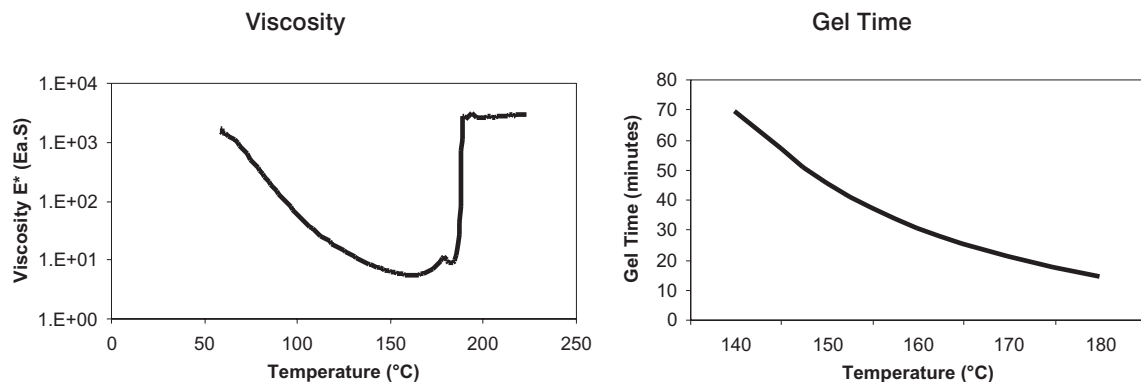

### Typical Neat Resin Data

Colour	Orange
Density	1.22 g/cm <sup>3</sup>
Glass Transition Temperature Tg Dry	196 °C
Glass Transition Temperature Tg wet 14 days in water @70°C	165 °C
Tensile Strength	66 MPa
Tensile Modulus	4.2 GPa
Tensile Strain	1.58 %
Poisson Ratio	0.40%
Linear coefficient of thermal expansion	55.10 <sup>-6</sup> °K <sup>-1</sup>
Fracture toughness, K <sub>1c</sub>	0.93 MPa.√m
Strain energy release rate, G <sub>1c</sub>	230 J/m <sup>2</sup>



## Prepreg Properties – HexPly® M18/1 UD and Woven Carbon Prepregs

### Physical Properties

	Units	42% G947 UD	43% G939 Fabric
Fibre Density	g/cm <sup>3</sup>	1.78	1.78
Filament count/tow		3000	3000
Resin Density	g/cm <sup>3</sup>	1.22	1.22
Fibre areal weight	g/m <sup>2</sup>	160	220
Nominal Cured Ply Thickness	mm	0.165	0.227
Nominal Fibre Volume	%	55	55

### Mechanical Properties


Test	Standard	Units	Temp (°C)	Condition UD	42% G947 Fabric	43% G939
0° Tensile Strength	EN2561	MPa	-55	Dry	1750	750
			RT	Dry	1750	800
			135	Wet	1700	800
90° Tensile Strength		MPa	RT	Dry	55	800
0° Tensile Modulus	EN2561	GPa	-55	Dry	127	67
			RT	Dry	128	65
			135	Wet	133	67
90° Tensile Modulus		GPa	RT	Dry	9.3	67
0° Compression Strength	EN2850 Type A	MPa	-55	Dry	1500	850
			RT	Dry	1200	800
			135	Wet	750	500
90° Compression Strength		MPa	RT	Dry	220	800
0° Compression Modulus	EN2850 Type A	GPa	-55	Dry	121	62
			RT	Dry	121	64
			135	Wet	121	63
90° Compression Modulus		GPa	RT	Dry	10.2	62
0° ILSS (Short beam shear)	EN2563	MPa	RT	Dry	95	70
			75	Wet	65	56
			135	Wet	50	40
In-plane Shear Strength	EN6031	MPa	RT	Dry	95	100
			75	Wet	90	85
			135	Wet	70	65

Wet : 1 week at 70°C 95% relative humidity (RH) and 3 weeks at 70°C 85% RH


These are values obtained on a 55% fibre volume content laminate (i.e. a cured ply thickness of approx. 0.165mm with G947 and 0.227 mm with G939).

### Curing Conditions


Monolithic Parts (autoclave)

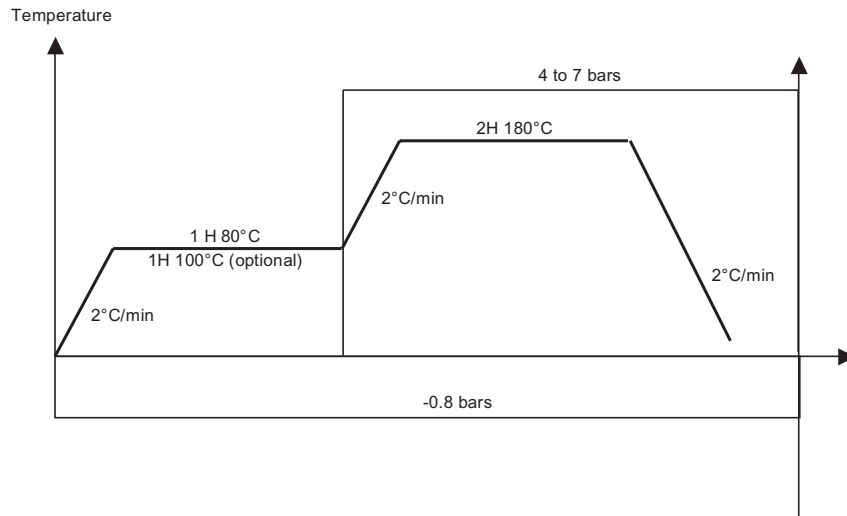

Sandwich parts (autoclave)

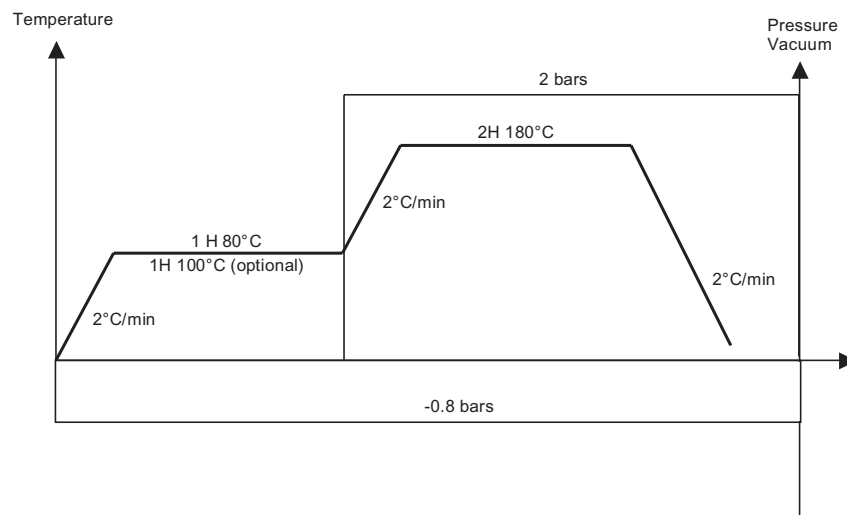

Vacuum bag cycle (monolithic and sandwich parts):

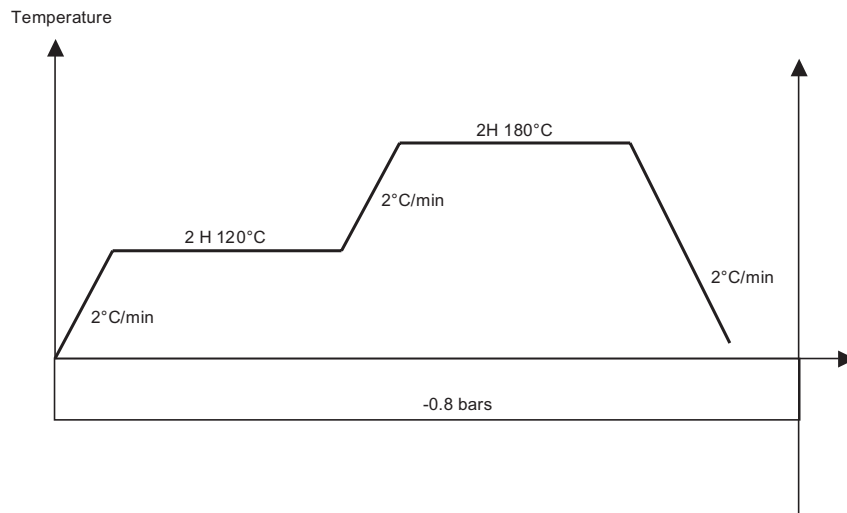



## Prepreg Storage Life

---

Tack Life:	13 days at RT (23°)
Out Life:	15 days at RT (23°C)
Shelf Life:	12 months at -18°C (from date of manufacture)

### Definitions:

Tack Life:	The time, at room temperature, during which prepreg retains enough tack for easy component lay-up.
Out Life:	The maximum accumulated time allowed at room temperature between removal from the freezer and cure.
Shelf Life:	The maximum storage for HexPly® Prepreg, upon receipt by the customer, when stored continuously, in a sealed moisture-proof bag, at -18°C. To accurately establish the exact expiry date, consult the box label.

HexPly® M18/1 prepregs should be stored as received in a cool dry place or in a refrigerator. After removal from refrigerator storage, prepreg should be allowed to reach room temperature before opening the polyethylene bag, thus preventing condensation (A full reel in it's packaging can take up to 48 hours).

### Important

All information is believed to be accurate but is given without acceptance of liability. Users should make their own assessment of the suitability of any product for the purposes required. All sales are made subject to our standard terms of sale which include limitations on liability and other important terms.

©Copyright Hexcel Corporation  
Publication FTA274a (March 2007)

### For More Information

Hexcel is a leading worldwide supplier of composite materials to aerospace and other demanding industries. Our comprehensive product range includes:

- Carbon Fibre
- RTM Materials
- Honeycomb Cores
- Continuous Fibre Reinforced Thermoplastics
- Carbon, glass, aramid and hybrid prepregs
- Reinforcement Fabrics
- Structural Film Adhesives
- Honeycomb Sandwich Panels
- Special Process Honeycombs

For US quotes, orders and product information call toll-free 1-800-688-7734

For other worldwide sales office telephone numbers and a full address list please go to:

<http://www.hexcel.com/contact/salesoffices>