



HexPly[®] M42

180°C curing epoxy matrix



Product Data Sheet

Description



HexPly[®] M42 is a high performance, self extinguishing, self adhesive, tough epoxy matrix for use in primary aerospace sandwich structures. It exhibits very high impact resistance and damage tolerance for a wide range of applications.

HexPly[®] M42 is a toughed epoxy resin system supplied with woven glass, carbon and hybrid glass/carbon fibres. HexPly[®] M42 was developed as a controlled flow system to operate in environments up to 120-130°C.

Benefits and Features

- Hot melt chemistry (nominal 180°C cure)
- Self extinguishing
- Self adhesive on honeycomb (autoclave or vacuum bag)
- Very high temperature wet performances (120°C wet continuous service temperature)
- Low moisture absorption (0.74% after 1 week at 70°C 95% relative humidity (RH) and 3 weeks at 70°C 85% RH, measured on carbon/glass fibre laminate)
- Flexible cure cycle (from 135°C to 210°C with or without post-cure)
- High damage resistance

Resin Matrix Properties

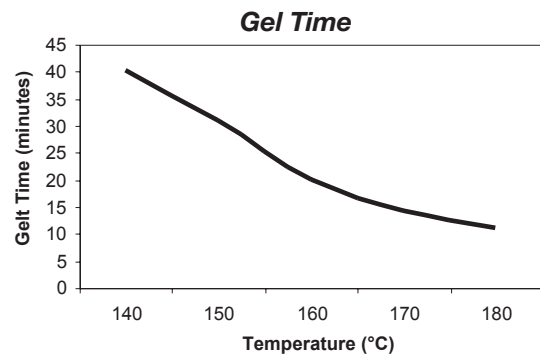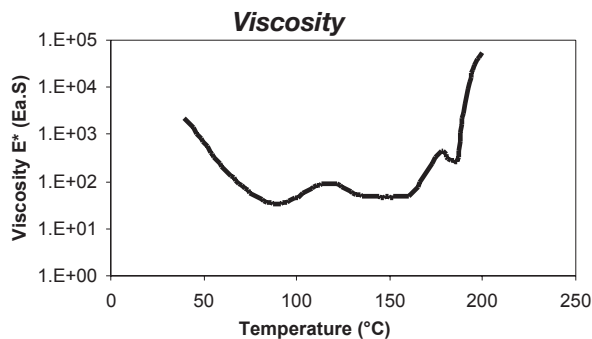

Cured Matrix Properties

Colour	Brown	
Density	1.26 g/cm ³	
Glass Transition T° (Dry)	190±5°C	DMA onset according to EN6032 (Single cantilever, 1Hz, 5µm)
Glass Transition T° (Wet)	150±5 °C	DMA onset according to EN6032 (Single cantilever, 1Hz, 5µm)
Tensile Strength	77 MPa	
Tensile Modulus	4.0 GPa	
Tensile Strain	1.59 %	
Poisson Ratio	0.40%	
Linear coefficient of thermal expansion	59.10 ⁻⁶ °K ⁻¹	
Fracture toughness, K1c	1.83 MPa.√m	
Strain energy release rate, G1C	990 J/m ²	

Wet Ageing using accelerated method, 14 days submerged in 70°C water



Prepreg Properties – HexPly® M42 Woven Carbon and Hybrid Prepregs

Physical Properties

	Units	52%/G1177 Glass/Carbon	63%/120 E-Glass	50%/G939 HS Carbon	54%/G1088 Glass/Carbon
Fibre Density	g/cm ³	2.1	2.6	1.78	2.25
Resin Density	g/cm ³	1.26	1.26	1.26	1.26
Fibre areal weight	g/m ²	185	107	220	135
Nominal Cured Ply Thickness	mm	0.21	0.15	0.22	0.11
Nominal Fibre Volume	%	42	35	55	53

Mechanical Properties

Test	Standard	Units	Temp (°C)	Condition	52%/G1177 HS Carbon	63%/120 E-Glass	50%/G939 HS Carbon	54%/G1088 Glass/Carbon
90° Tensile Strength	EN2561	MPa	RT	Dry	400	280	850	377
			23	Wet	370	-	-	-
			130	Wet	320	-	-	-
			135	Wet	-	-	750	-
90° Tensile Modulus		GPa	RT	Dry	38	17	62.8	28
			23	Wet	37	-	-	-
			130	Wet	37	-	--	-
			135	Wet	-	-	60.0	-
90° Compression Strength	EN2850 Type B	MPa	RT	Dry	650	-	730	-
			23	Wet	590	-	-	-
			130	Wet	390	-	-	-
			135	Wet	-	-	530	-
90° Compression Modulus		MPa	RT	Dry	37	-	-	370
			23	Wet	38	-	-	-
			130	Wet	36	-	-	-
0° ILSS	EN2563 Short beam shear	MPa	RT	Dry	-	55	65	48
			120	Dry	-	-	49	-
			135	Wet	-	-	35	32
			150	Wet	-	-	-	27
90° ILSS			RT	Dry	68	49.7	-	-
			130	Wet	34	-	-	-
			150	Wet	31	-	-	-
In-plane Shear Strength	EN 6031	MPa	RT	Dry	79	-	-	108
			100	Wet	54	-	-	-
			130	Wet	48	-	-	-
			150	Wet	-	-	-	58
In-plane Shear Modulus		GPa	RT	Dry	3.58	-	-	3.0
			100	Wet	-	-	-	-
			130	Wet	2.4	-	-	2.0
			150	Wet	-	-	-	-
Climbing Drum Peel	EN 2243-3	MPa	RT	Dry Top	-	-	49	47
			RT	Dry Bottom	-	-	59	53


Wet : 1 week at 70°C 95% relative humidity (RH) and 3 weeks at 70°C 85% RH

These are values obtained for G1177 with 0.21mm/ply, for 120 with 0.115mm/ply, for G939 with 0.22mm and for G1088 with 0.11mm.





Curing Conditions

Monolithic Parts (autoclave)

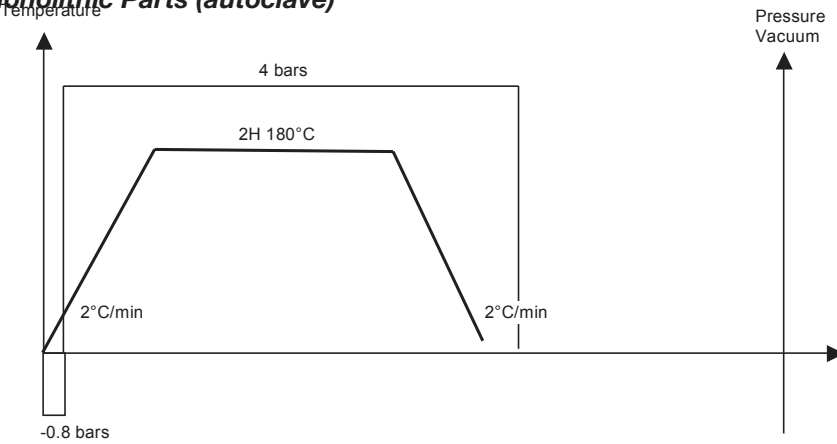

Sandwich parts (autoclave)

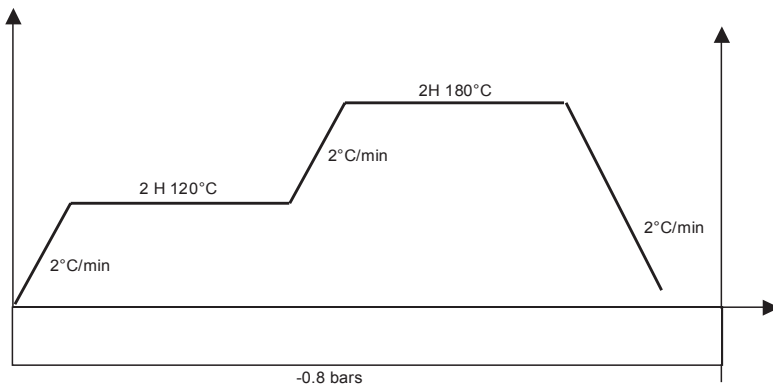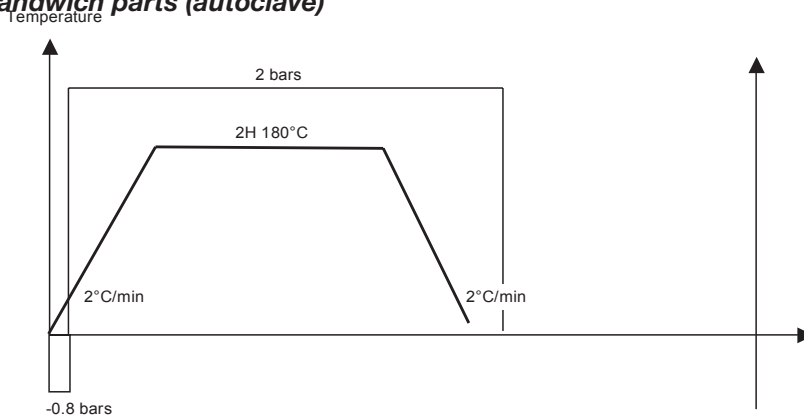



HexPly® M42

180°C curing epoxy matrix



Product Data Sheet

Prepreg Storage Life

Out Life: 18 days at RT (23°C)
Shelf Life: 12 months at -18°C (from date of manufacture)

Definitions:

Out Life: The maximum accumulated time allowed at room temperature between removal from the freezer and cure.

Shelf Life: The maximum storage life for HexPly® prepreg, when stored continuously, in a closed moisture-proof bag, at -18°C. To accurately establish the exact expiry date, consult the box label.

HexPly® M42 prepregs should be stored as received in a cool dry place or in a refrigerator. After removal from refrigerator storage, prepreg should be allowed to reach room temperature before opening the polyethylene bag, thus preventing condensation (A full reel in its packaging can take up to 48 hours).

For more information

Hexcel is a leading worldwide supplier of composite materials to aerospace and industrial markets. Our comprehensive range includes:

- HexTow® carbon fibers
- HexMC®-i molding compounds
- HexWeb® honeycombs
- HexForce® reinforcements
- HexFlow® RTM resins
- Acousti-Cap® sound attenuating honeycomb
- HiMax® multiaxial reinforcements
- HexBond™ adhesives
- Engineered core
- HexPly® prepregs
- HexTool® tooling materials
- Engineered products

For U.S. quotes, orders and product information call toll-free 1-800-688-7734. For other worldwide sales office telephone numbers and a full address list, please go to:

<https://www.hexcel.com/contact>

©2026 Hexcel Corporation – All rights reserved. Hexcel Corporation and its subsidiaries (“Hexcel”) believe that the technical data and other information provided herein was materially accurate as of the date this document was issued. Hexcel reserves the right to update, revise or modify such technical data and information at any time. Any performance values provided are considered representative but do not and should not constitute a substitute for your own testing of the suitability of our products for your particular purpose. Hexcel makes no warranty or representation, express or implied, including but not limited to the implied warranties of merchantability and fitness for a particular purpose, and disclaims any liability arising out of or related to, the use of or reliance upon any of the technical data or information contained in this document.